

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YYYY) 18 March 2016		2. REPORT TYPE Briefing Charts		3. DATES COVERED (From - To) 24 February 2016 – 18 March 2016	
4. TITLE AND SUBTITLE Predictive methods for dense polymer networks: Combating bias with bio-based structures				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Andrew J. Guenther; Benjamin G. Harvey; Michael D. Ford; Josiah T. Reams; Joseph M. Mabry				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER Q16J	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Air Force Research Laboratory (AFMC) AFRL/RQRP 10 E. Saturn Blvd. Edwards AFB, CA 93524-7680				8. PERFORMING ORGANIZATION REPORT NO.	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Research Laboratory (AFMC) AFRL/RQR 5 Pollux Drive Edwards AFB, CA 93524-7048				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S) AFRL-RQ-ED-VG-2016-055	
12. DISTRIBUTION / AVAILABILITY STATEMENT Approved for Public Release; Distribution Unlimited.					
13. SUPPLEMENTARY NOTES For presentation at American Chemical Society 251st National Meeting; San Diego, CA (16 March 2016) PA Case Number: #16152; Clearance Date: 3/18/2016					
14. ABSTRACT Viewgraph/Briefing Charts					
15. SUBJECT TERMS N/A					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT SAR	18. NUMBER OF PAGES 19	19a. NAME OF RESPONSIBLE PERSON A Guenther
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NO (include area code) N/A

Predictive methods for dense polymer networks: Combating bias with bio-based structures

16 March 2016

Andrew J. Guenthner,¹ Benjamin G. Harvey,²
Michael D. Ford,³ Josiah T. Reams,³ Joseph
M. Mabry¹

¹*Air Force Research Laboratory, Rocket Propulsion
Division*

Edwards AFB, CA 93524

andrew.guenthner@us.af.mil

²*Naval Air Warfare Center, Weapons Division*

³*ERC Incorporated*



Integrity ★ Service ★ Excellence



Outline



- Background: Polymer Networks / Cyanate Esters
- Architectural Bias
- Comparison of Petroleum-Based and Bio-Based Chemical Architectures
- Continuing Research on Structure-Property Relationships using Informatics Tools



Acknowledgements: Air Force Office of Scientific Research, Air Force Research Laboratory, Office of Naval Research, Strategic Environmental Research & Development Program – Program Support




Applied Materials Group



- Dr. Jeffrey Alston
- Mr. Michael Ford
- Mr. Kevin Greeson
- Dr. Andrew Guenther
- Dr. Timothy Haddad
- Mr. Jason Lamb
- Mr. Christopher Lee


- Dr. Joseph Mates
- Mr. Jacob Marcischak
- Dr. Josiah Reams
- Mr. Neil Redeker
- Dr. Gregory Yandek
- Mr. Jacob Zavala

amg

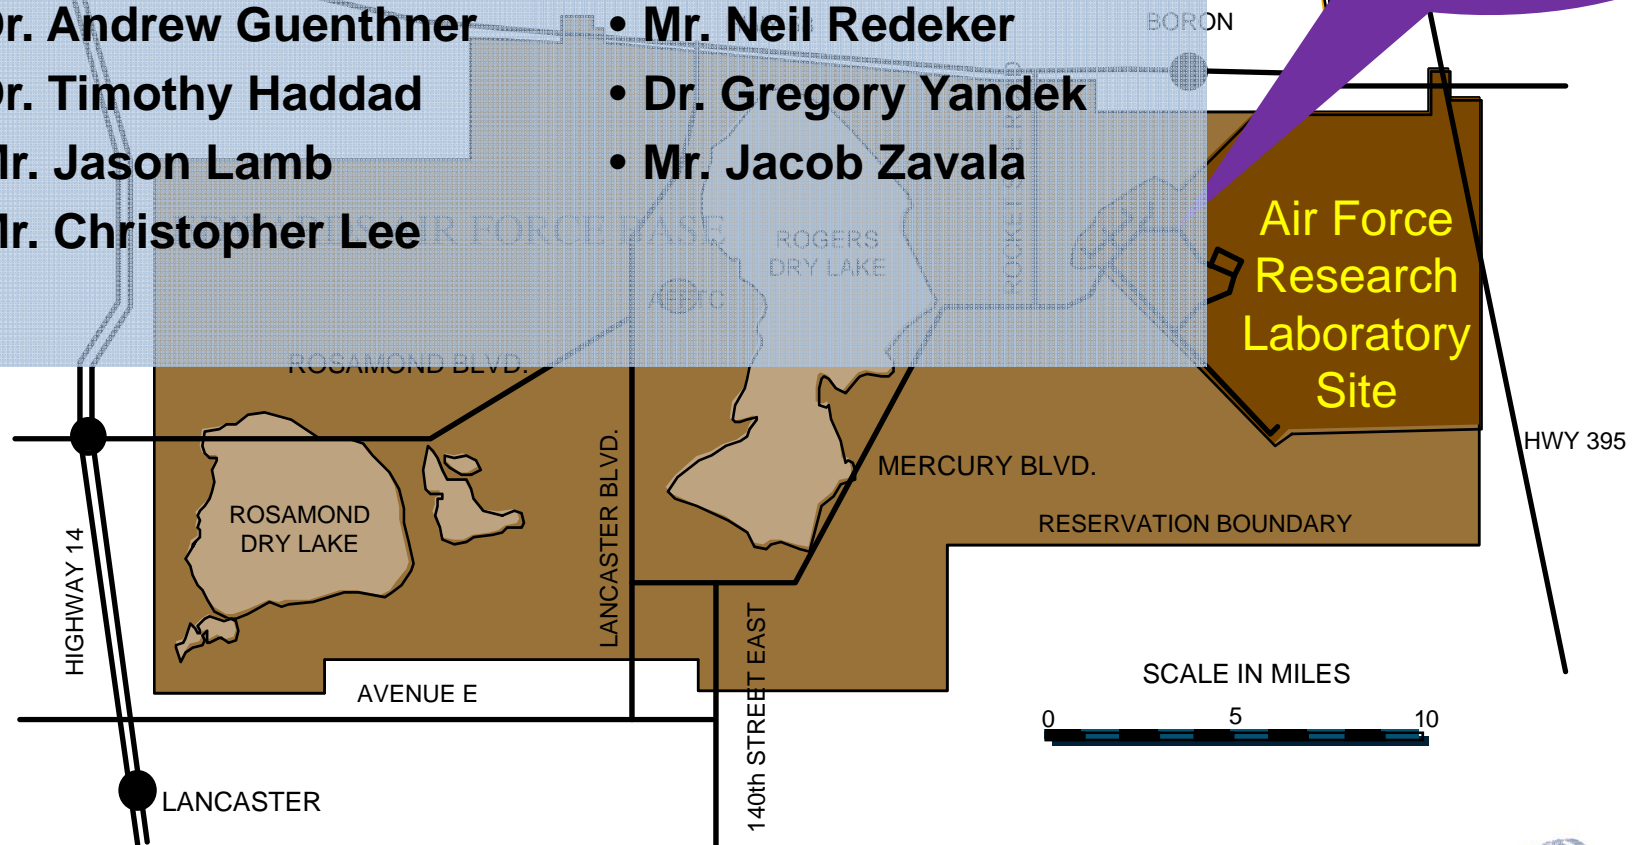



Model High-Temperature Thermosetting Polymer Networks: Cyanate Esters

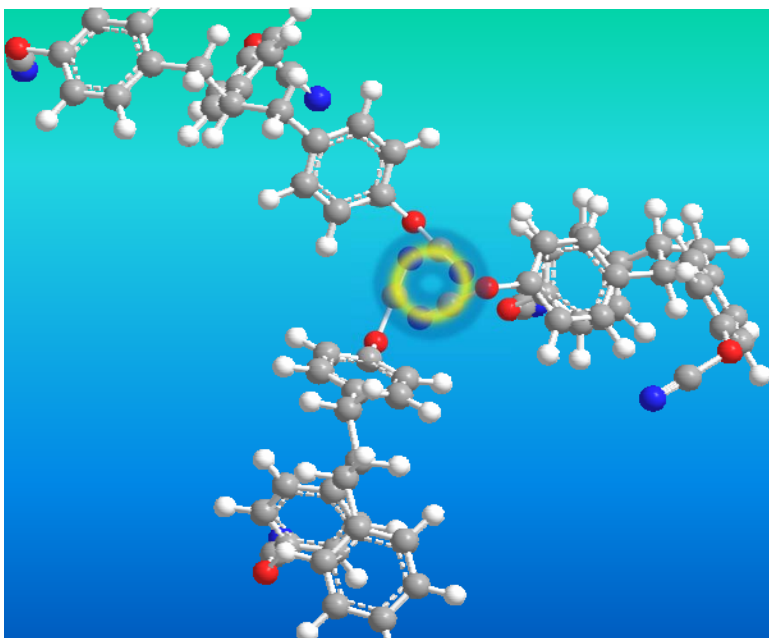

Principal reaction:



Selectivity: 80% - > 98%

$\Delta H_f = -110 \text{ kJ / eq.}$

Conversion kinetics; Auto-catalytic
(may be catalyzed)


Typical conversion rate: ~50%/hr
(max) at 250 °C (uncatalyzed)

Extend of conversion: Limited to $T_G =$
 $T_{cure} + 30\text{-}60 \text{ }^\circ\text{C}$

- A single, known reaction predominates.
- Methods for assessing the extent of side reactions, and for minimizing side reactions, are known.
- The structure of even fully cured networks is easily analyzed and described quantitatively.
- Samples are easy to prepare in the laboratory; cure conditions are readily manipulated over a very wide range of rates.



Applications of Polycyanurate Networks

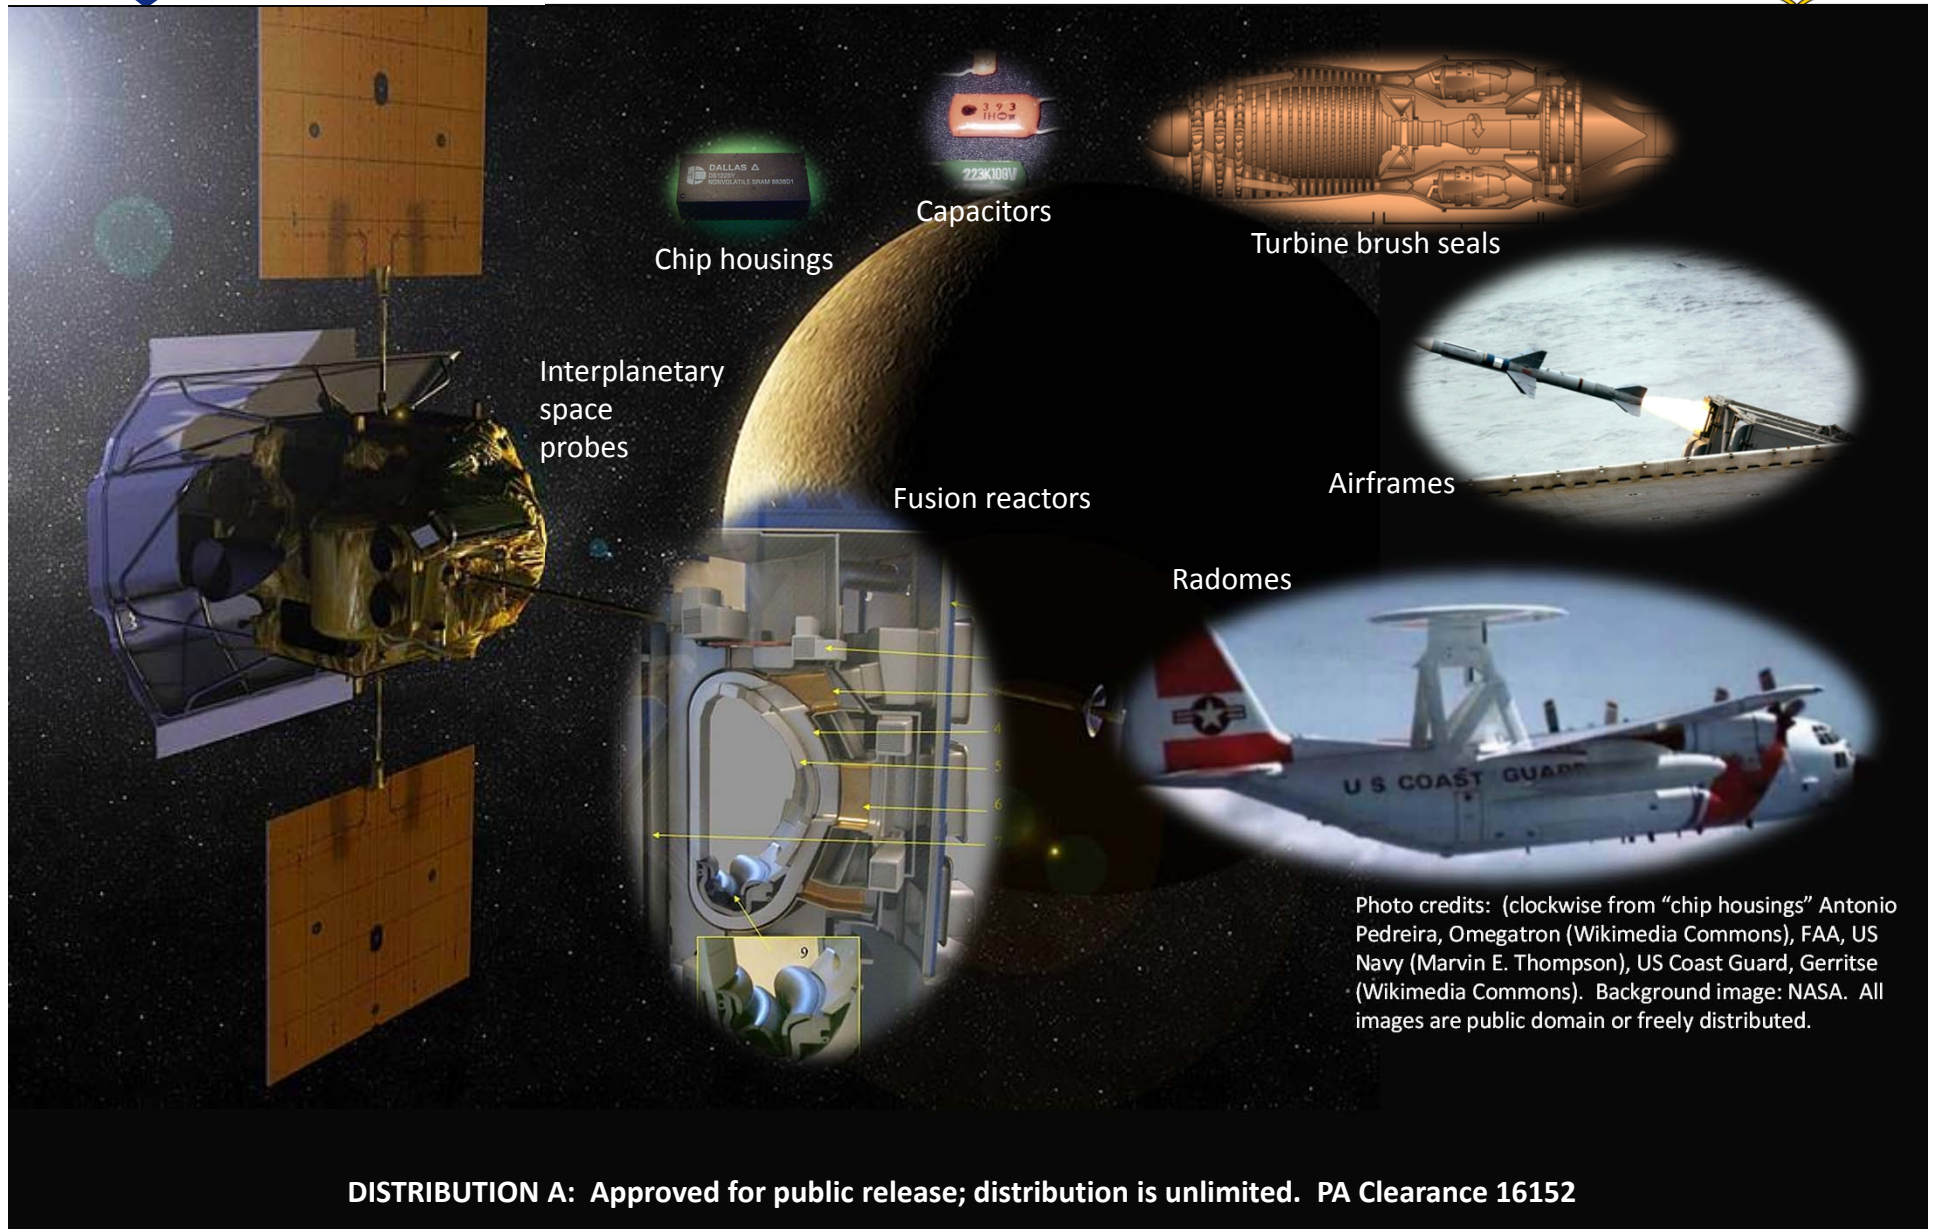


DISTRIBUTION A: Approved for public release; distribution is unlimited. PA Clearance 16152




Describing Polymer Networks: Structure – Architecture – Topology





Structures

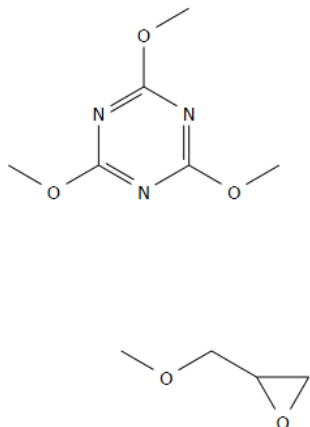

Architectures

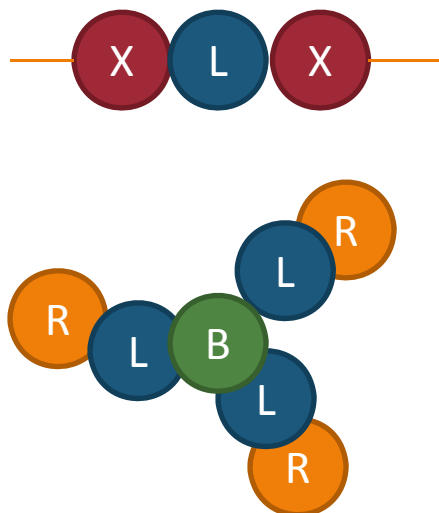

Topologies

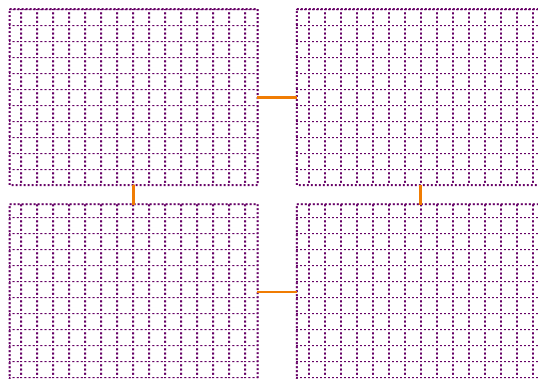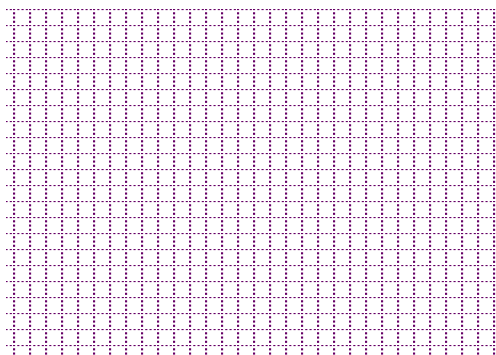


- **Networks tend to be described by three levels of hierarchy**
 - **Chemical structure** usually refers to the number, type, and geometric relationship of atoms in repeated groups
 - **Chemical architecture** describes the number, type, and geometric interconnection of repeated structures
 - **Network topology** in this context describes the number, type, and geometric relationship of repeated architectural units


Most heuristic “structure-property” methods concentrate on chemical structure only



Example: Bias in Predictive Parameter Sets

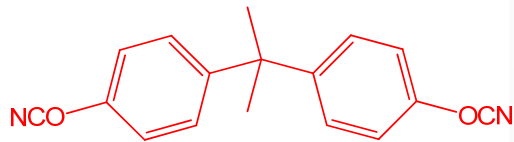


BADCy

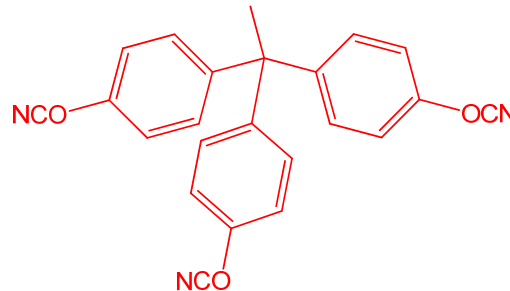

ESR255

All samples were melted, blended, and de-gassed for 30 min. prior to cure in silicone molds under N₂, cure schedule for 1 hr at 150 °C followed by 24 hrs at 210 °C, with ramp rates at 5 °C / min.

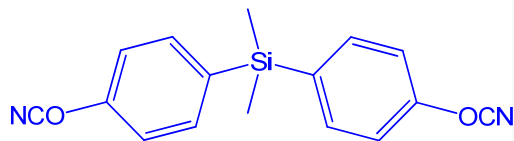

SiMCy



STT3

In this case, we are interested in comparing models for two different architectures, one very common, the other somewhat rare



Comparison of Predicted and Experimental Melting Properties




ΔS_m (kJ/mol K, monomer)	BADCy	SiMCy	ESR255	STT3
ΔS_m (kJ/mol K, Yalkowsky)	84	84	98	98
ΔS_m (kJ/mol K, experiment)	80.0 ± 1.4	82.1 ± 0.6	75.0 ± 1.9	74.8 ± 0.8
ΔS_m^0 (kJ/mol K, Chickos)	70	78	88	95
ΔS_m^0 (kJ/mol K, experiment)	69 ± 3	81 ± 1	50 ± 14	55 ± 3
T_m (model ΔS_m & exp. ΔH_m)				
Yalkowsky (°C)	66	54	24	24
Chickos (°C)	73	50	42	29
Experiment (°C)	82.1 ± 0.2	60.4 ± 0.1	115.9 ± 0.2	117.5 ± 0.1

- Yalkowsky model over-predicts entropy of melting for tricyanates, in part because the rules for counting anisotropy do not consider star-like arrangements, and a triphenyl substituted sp^3 is still counted as flexible. These factors explain about 70% of the error.
- Chickos model has a similar pattern of predictive success, perhaps because “bis-like” prolate organic compounds are more studied than “tris-like” “pitchfork” structures

Conversion from ΔS_m^0 to ΔS_m based on $\Delta_{cp,m} = \text{const.} = \Delta S_m$; $\Delta S_m = \Delta S_m^0 / [1 - \ln (T_m / 298)]$



Factors that Introduce Architectural Bias in Structure-Property Relationships

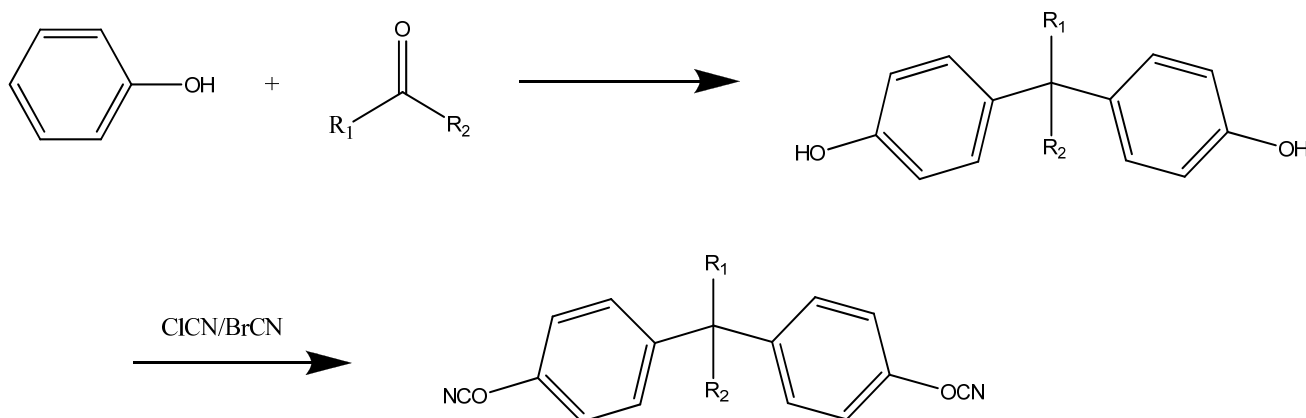


- The vast majority of monomers containing phenol groups are made by catalytic coupling of phenol, either to produce bisphenol or novolac (phenol-formaldehyde) structures, as a result of an inexpensive supply of phenol from petroleum refining.

Consequently, certain architectures are over-represented in a “random” sample of network-forming phenolic monomers.




Bio-Based Phenols: Wide Range of Sources and Methods

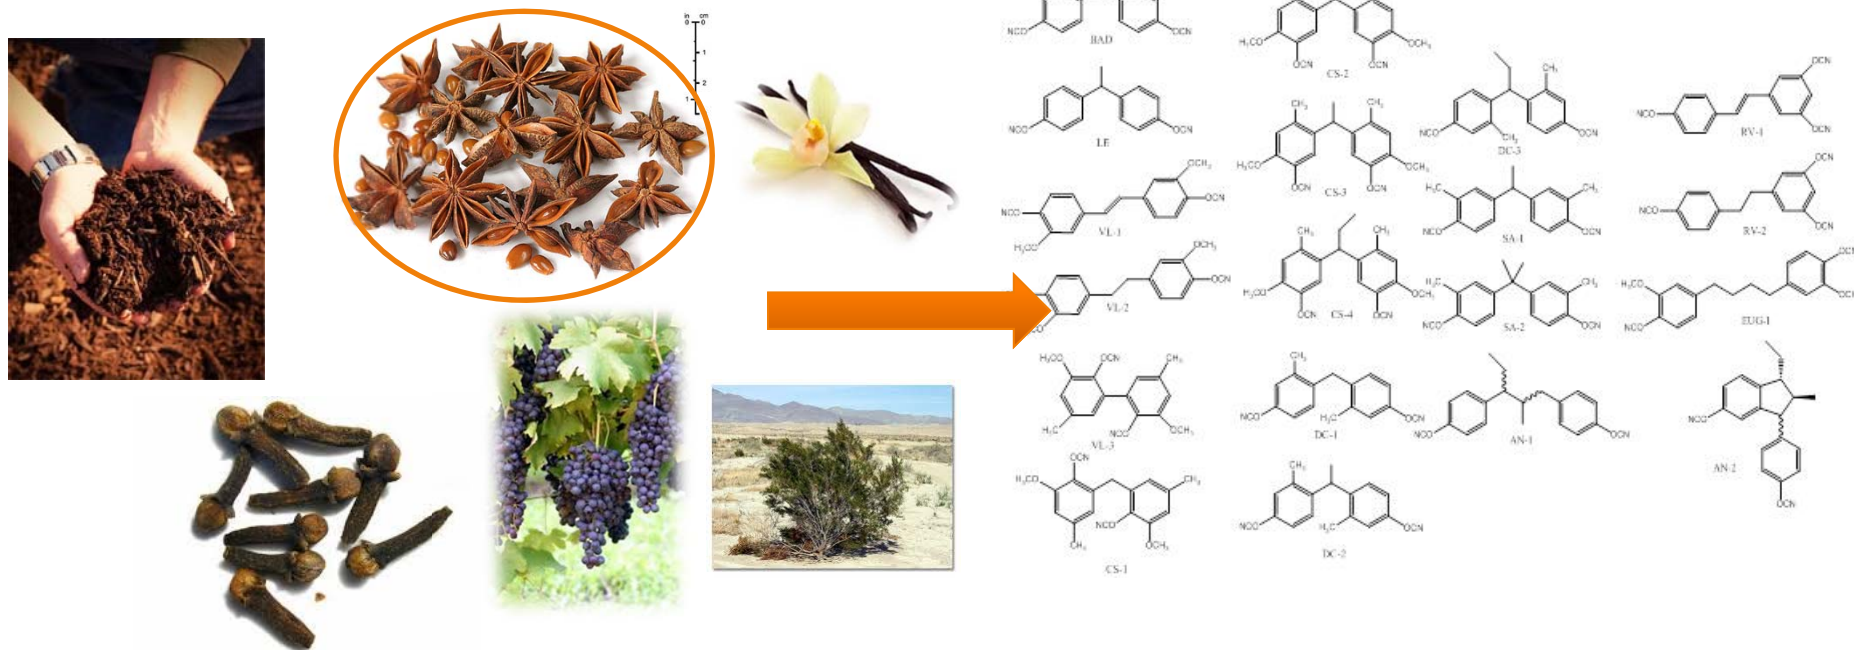

- Bio-based cyanate esters have been made from anethole, resveratrol, eugenol, cresol, lignin, vanillin, and even creosote oils. A much wider array of structures can be accessed from these sources than is available from refining petroleum



Quantification of Cyanate Ester Structural Factors

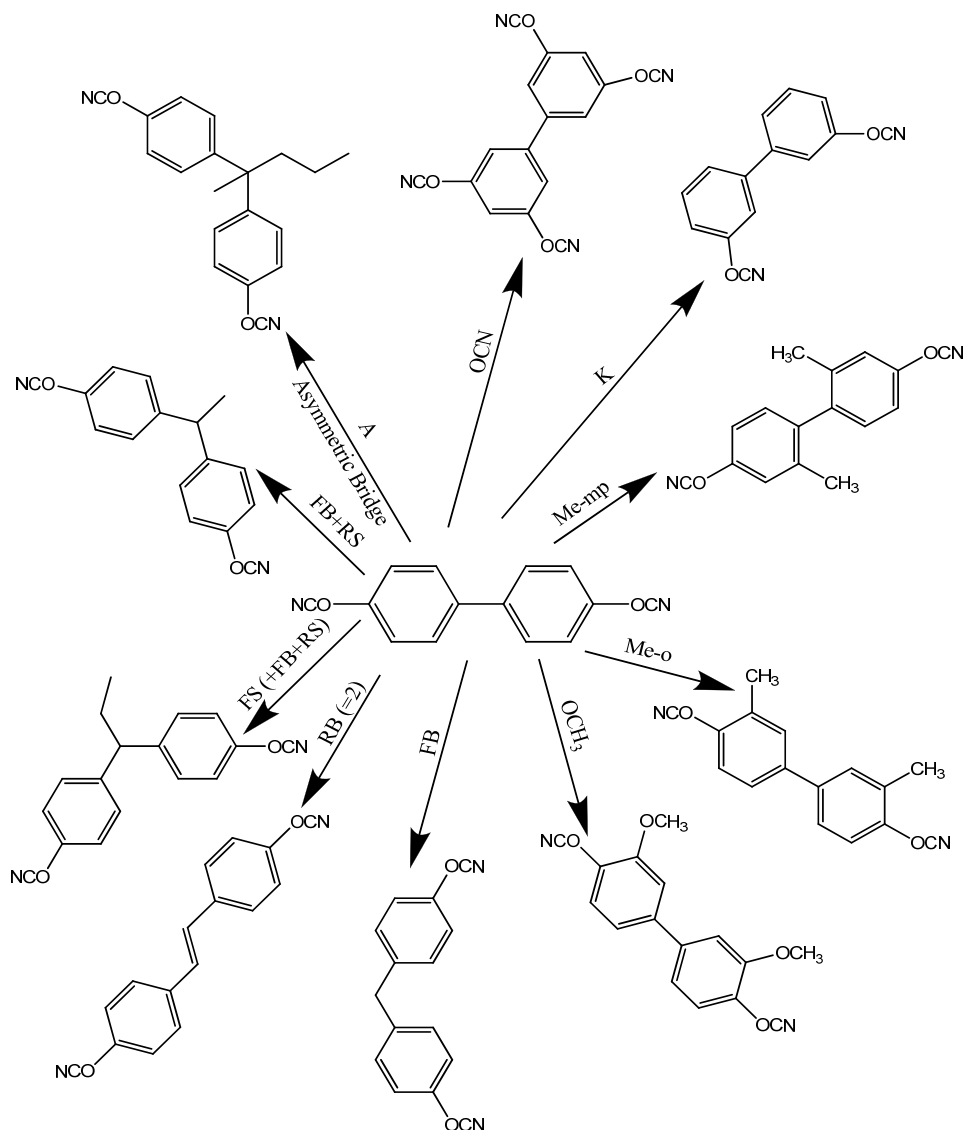

Monomer	OCN	K	Me-mp	Me-o	OCH3	FB	RB	FS	RS	A
BAD	0	0	0	0	0	1	0	0	2	0
LE	0	0	0	0	0	1	0	0	1	1
AN-1	0	0	0	0	0	3	0	1	2	1
AN-2	0	0	0	0	0	0.5	0.5	1.5	3.5	1
CS-1	0	1	1	0	1	1	0	0	0	0
CS-2	0	1	1	0	1	1	0	0	0	0
CS-3	0	1	1	0	1	1	0	0	1	1
CS-4	0	1	1	0	1	1	0	1	1	1
DC-1	0	0	1	0	0	1	0	0	0	0
DC-2	0	0	1	0	0	1	0	0	1	1
DC-3	0	0	1	0	0	1	0	1	1	1
EUG-1	0	0	0	0	1	4	0	0	0	0
RV-1	1	0.5	0	0	0	0	2	0	0	0
RV-2	1	0.5	0	0	0	2	0	0	0	0
SA-1	0	0	0	1	0	1	0	0	1	1
SA-2	0	0	0	1	0	1	0	0	2	0
VL-1	0	0	0	0	1	0	2	0	0	0
VL-2	0	0	0	0	1	2	0	0	0	0
VL-3	0	1	1	0	1	0	0	0	0	0
AN-U	0	0	0	0	0	1	2	1	2	1
EUG-U	0	0	0	0	1	2	0	0	0	0

The structure of bio-based monomers and networks with an X-L-X architecture (X = phenyl cyanate ester / phenyl cyanurate) is quantified using 10 parameters



Property Data for Cyanate Ester Monomers and Networks



Monomer/net work	T _m (°C) ^a	T _{G-fc} (°C) ^b	Char Yield (N ₂ , %)	Char Yield (Air, %)
BAD	83	323	47	25
LE	Liquid ^c	295	54	24
AN-1	Liquid ^c	223	31	9
AN-2	72	313	48	6
CS-1	151	236	33	8
CS-2	125	240	35	11
CS-3	98	206	28	11
CS-4	120	238	27	11
DC-1	88	259	53	30
DC-2	105	283	43	4
DC-3	Liquid ^c	273	43	3
EUG-1	104	167	31	1
RV-1	156	>340	74	71
RV-2	123	334	70	66
SA-1	73	236	48	11
SA-2	82	237	43	8
VL-1	237	n/a	n/a	n/a
VL-2	190	n/a	n/a	n/a
VL-3	205	n/a	n/a	n/a


Although this data set is not large by informatics standards, it nonetheless represents a significant amount of synthetic effort.

Because the data is limited, minimizing bias by investigating a wide variety of structures is important.

Four properties that have been measured and published using a well-defined, robust, and identical technique for all examples were chosen to examine predictive models.



Predictive Models: Partial Least Squares Approach

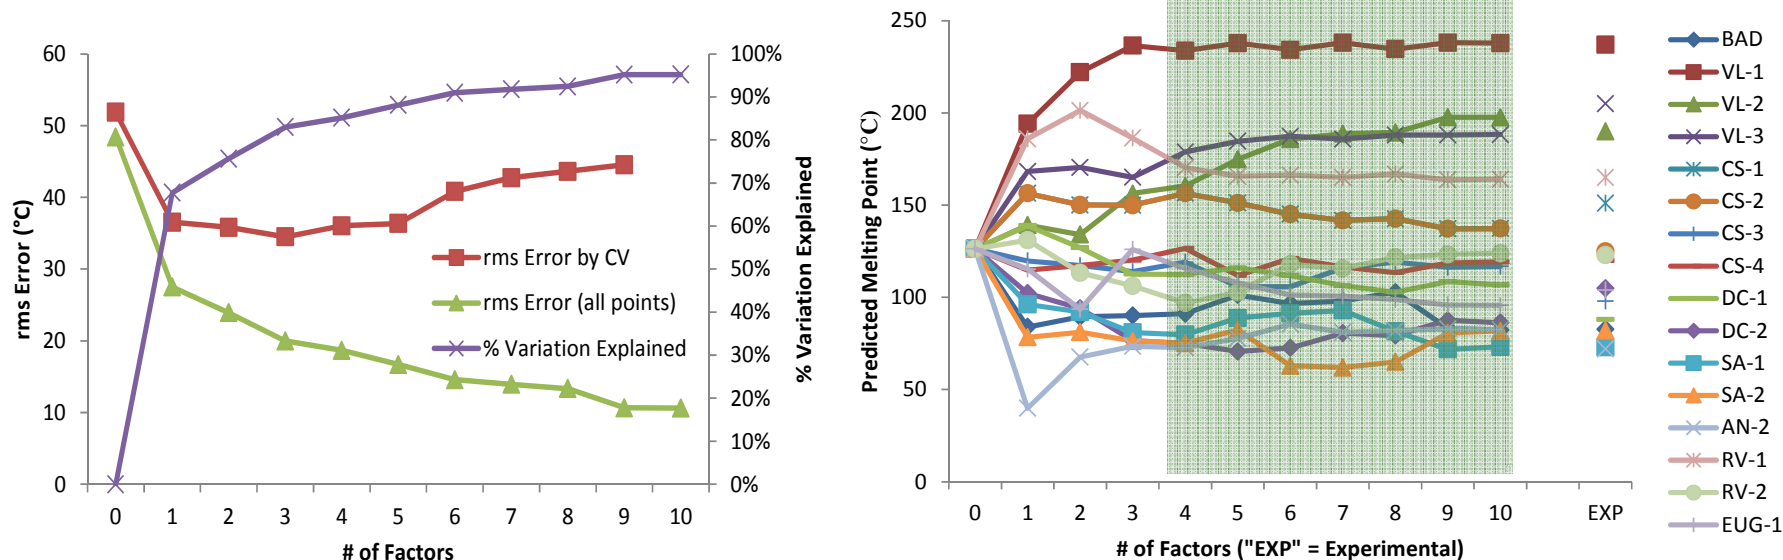


Informatics techniques like partial least squares provide methods to avoid issues associated with over-prediction when many structural variables are present

In this instance, cross-validation (leave-one-out) is utilized to establish the number of factors needed for prediction of melting points of X-L-X type cyanate ester monomers



Effect of Over-Prediction on Model Regression Coefficients

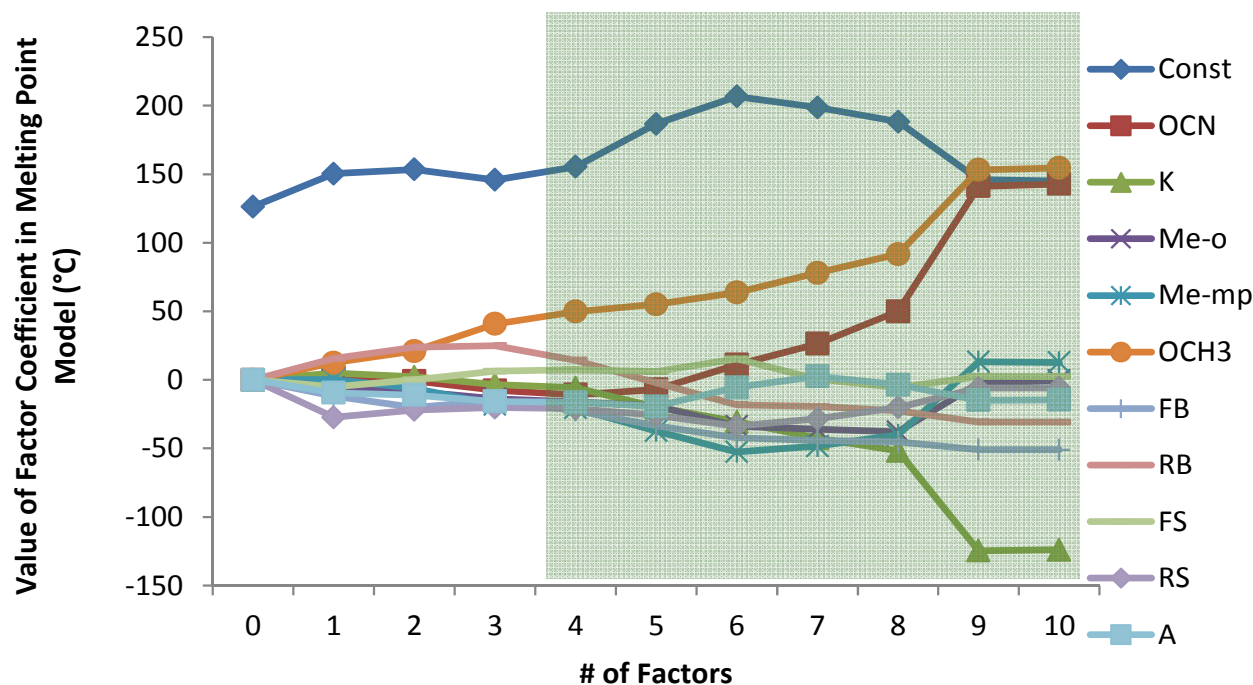

Factor	PLS	OLS
Constant	145.88	144.97
OCN	-7.64	142.86
K	-3.44	-123.97
Me-o	-13.73	-0.42
Me-mp	-18.07	12.73
OCH3	40.74	154.55
FB	-15.17	-50.97
RB	24.92	-30.87
FS	6.21	2.37
RS	-20.27	-5.86
A	-15.69	-14.60

Generally, the structural changes represented by each unit change in each parameter are relatively minor. Their effect on melting point, as represented by the value of the regression coefficient, is also expected to be minor.




Analysis of the regression coefficient values therefore provides a way to detect over-prediction.



Actual Melting Point Predictions



Liquid at room temp Not yet synthesized

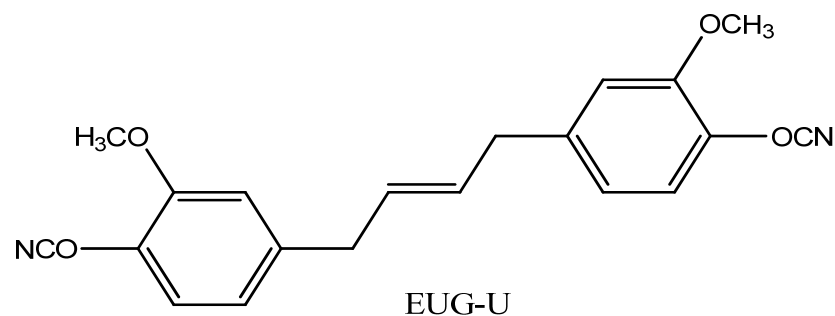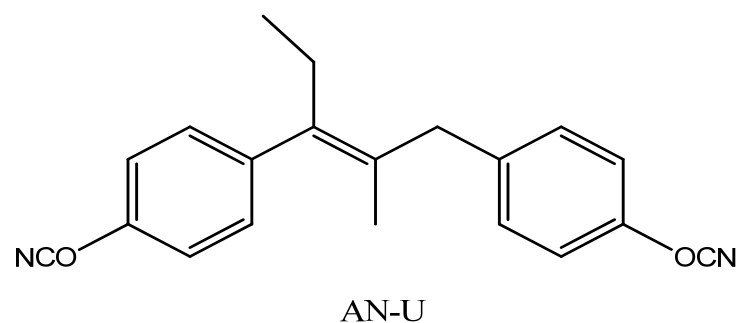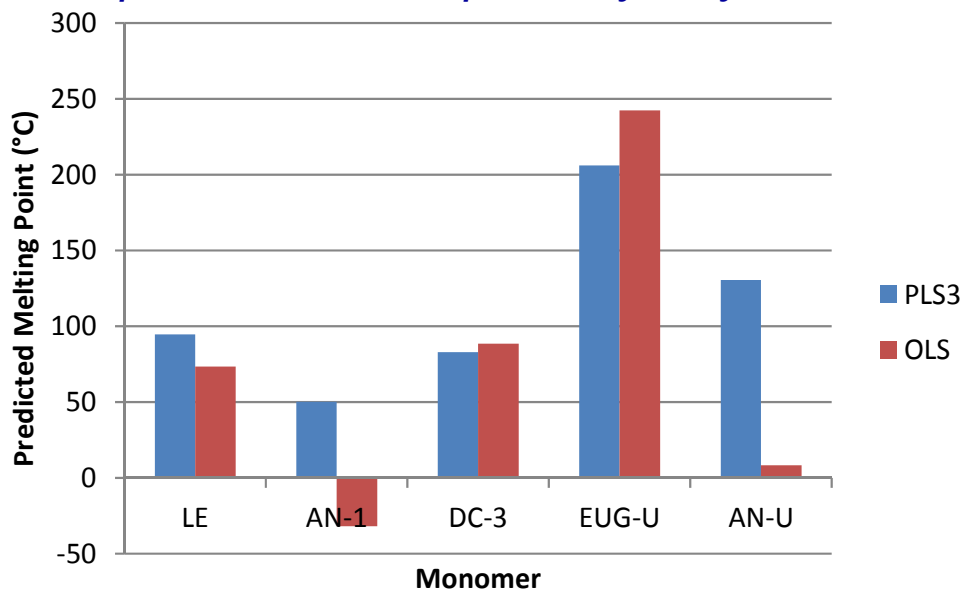

Useful models should indicate a low melting point for monomers that are liquids (often supercooled with a melting point of up to 70 °C) at ambient temperature.



The compounds “EUG-U” and “AN-U” were not synthesized prior to model construction, and are being used as tests of genuine predictive power.



Actual Melting Point Predictions with Experimental Data



Method for Predicting Melting Point ...	Prediction for LECy	Prediction for EUG-U
Partial Least Squares	95	206
Ordinary Least Squares	74	242
Measured (Lit. / DSC)	29	107

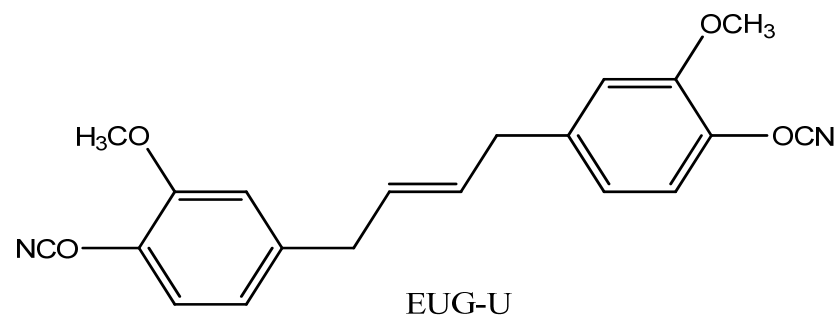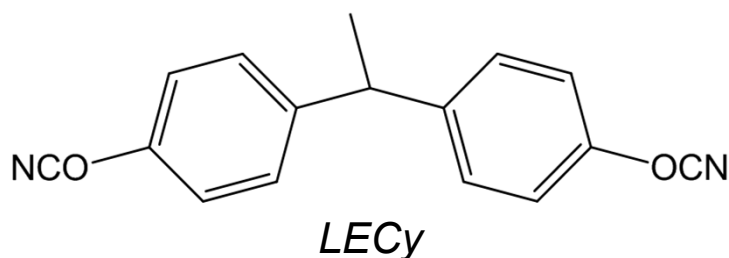



Summary



- **Property prediction in polymer networks involves consideration of chemical structure, chemical architecture, and network topology**
- **The effectiveness of traditional chemical structure-property relationships for prediction of properties is often compromised by bias toward certain chemical architectures, a factor which is not adequately captured in the usual structural parameters**
- **The use of biologically-derived chemical structures in building structure-property relationships can often help to ensure that a wide range of structures, architectures, and even network topologies are incorporated in the correlations**
- **The use of informatics techniques on relatively small data sets used to build improved structure-property correlations for polymer networks is an area of continuing research**

